

Modification of Montmorillonite by New Surfactants

Mansor B. Ahmad, Wisam H. Hoidy, Nor Azowa Bt Ibrahim and Emad A. Jaffar Al-Mulla
Department of Chemistry, Faculty of Science, Putra Malaysia University,
43400 UPM Serdang, Selangor, Malaysia

Abstract: The sodium Montmorillonite is not susceptible to polymer due to its organophobic character and has low basal spacing. This study reports on the effect of three new organic cations including Triethyl Amine (TEA), Tripropyl Amine (TPA) and Trioctyl Amine (TOA) on the basal spacing of the clay as indicators to the sociability of the clay to the incorporation of polymers. The Fourier Transform Infrared spectroscopy (FTIR) was used to evaluate the incorporation of the three organic cations in the clay. The X-ray diffraction technique was utilized to indicate the basal spacing of the treated clay as a measure of the susceptibility of new organoclays. The FTIR, XRD and CHNS elemental analysis results shown that the three new organic cations acrylonitrile/montmorillonite were successfully incorporated in the Montmorillonite clay. X-ray diffraction indicates that the basal spacings in acrylonitrile/montmorillonite of the treated clay with TEA, TPA and TOA individually increased by 14.2, 15.1 and 19.5Å, respectively. FTIR spectra illustrate that amine compounds were successfully intercalated into the clay layers.

Key words: Sodium montmorillonite, triethyl amine, tripropyl amine, trioctyl amine, modification, surfactants, organic cations

INTRODUCTION

Sodium Montmorillonite are widely used in various science fields due to their large cation exchange capacity, high specific surface area, good swelling capacity and high platelet aspect ratio and ease with which their surface can be modified (He *et al.*, 2007a, b). Presence of inorganic cations such as Na⁺ and Ca²⁺ on the basal planar surface of montmorillonite layers makes it hydrophilic in nature and hence, shows the clay ineffective for absorption of aliphatic and relatively hydrophobic compounds (Kim *et al.*, 2003; Xie *et al.*, 2001). However, cation-exchange reactions have been traditionally exploited as an effective method to replace these inorganic ions with organic cationic surfactant molecules, which intercalate into the clay gallery, resulting in expansion of the interlayer spacing and leading to an increase in the basal spacing. These organic cations render the surface of the clay mineral hydrophobic, leading to the increase of the clay wettability and providing favourable interactions with organic molecules. Both organic-modified and unmodified clays have been used for different industrial applications such as rheological additives, thickeners in coating products, glues, plastisols, drilling fluids and cosmetics (Jaynes and Boyd, 1991). Recently, clays were used in the field of

materials science such as solid phase polymeric nanocomposites. In the 1990's, the use of organically modified clays in the polymer-clay nanocomposites has attracted researchers into this area of materials science and technology (Kojima *et al.*, 1993; Zhang and Wilkie, 2003). The organic modification of clay minerals leads to a decrease in surface energy making clays compatible with polymers. The surface energy of clay minerals and polymer can be determined from contact angle measurements (Maiti and Bhowmick, 2005). Stretz *et al.* (2005) reported that melt processed nylon 6-clay nanocomposites was prepared using organoclay, which contains methyl tallow bis 2-hydroxyethyl quaternary ammonium ions. Based on X-ray diffraction analysis, various arrangements of alkyl chains in organoclays had proposed by Lagaly (1986) Novel organo-montmorillonites have been synthesized and characterized using different ammonium compounds (Rajkiran and Kartic, 2008; Arroyo *et al.*, 2003). Series of anion-cation surfactants modified organoclays were prepared by incorporating of cationic surfactant hexadecyltrimethyl ammonium bromide and anionic surfactant, sodiumdodecyl sulfonate to montmorillonite (Chen *et al.*, 2008; Magaraphan *et al.*, 2001). In this study, three different aliphatic ammonium compounds, namely Triethyl Amine (TEA), Tripropyl Amine (TPA) and Trioctyl Amine


(TOA) were used to modify the compatibility of montmorillonite clay with polymers. These organo-montmorillonites can be used in various research and industrial applications.

MATERIALS AND METHODS


Materials: Sodium montmorillonite (Kunipia F) used in this study was obtained from Kunimine Ind. Co. Japan. The triethylamine, tripropylamine and trioctylamine, (Sigma-Aldrich), Germany. Hydrochloric acid from J.T. Baker, USA.

Preparation of organoclays (OMMTs): The OMMTs were prepared by dissolving 2.2 mL of concentrated HCl and amine compound in 800 mL of 80°C distilled water and Na⁺-MMT was dispersed in 600 mL hot water. The first solution was poured in MMT-water and vigorously stirred for 1 h. The white precipitation was filtered in a suction filtration and washed several times with distilled hot water till chloride ions completely removed. Then, the precipitation was dried in a vacuum oven at 80°C for 24 h. Table 1 shows, the structures of the three organoclays.

Ionization of TEA:




Cation exchange:




where, (C₂H₅)₃N⁺ and MMT-NH(C₂H₅)₃ are TEA and TEA-MMT, respectively.

Ionization of TPA:




Cation exchange:



where, (C₃H₇)₃N⁺ and MMT-NH(C₃H₇)₃ are TPA and TPA-MMT, respectively.

Ionization of TOA



Cation exchange




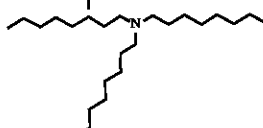


Table 1: The structures of the three organoclays

| Name of organoclay | The structure |
|----------------------|---|
| Triethylamine (TEA) |  |
| Tripropylamine (TPA) |  |
| Trioctylamine (TOA) |  |

where, (C₈H₁₇)₃N⁺ and MMT-NH(C₈H₁₇)₃ are TOA and TOA-MMT, respectively.

Characterizations: Organoclay were characterized using three different techniques including Fourier Transform Infrared spectroscopy (FTIR), (CHNS analyzer) and X-Ray Diffraction (XRD).

Fourier transform infrared spectroscopy: The FTIR spectrum was recorded on Perkin Elmer FTIR 1650 spectrophotometer at ambient temperature using a KBr disk method. The disk containing 0.0010 g of the sample and 0.3000 g of fine grade KBr was scanned at 16 scans at wave number range of 400-4000 cm⁻¹.

CHNS analysis: CHNS analyzer (LECO CHNS-932) was used for quantitative analysis of amount of intercalation agent present in the organoclay. A sample of approximately 2 mg of organocly burned at 1000°C under oxygen gaseous flow was used for this test. The sulfamethazine was used as standard.

X-Ray Diffraction (XRD): X-Ray Diffraction (XRD) study was carried out using Shimadzu XRD 6000 diffractometer with Cu-K θ-radiation (λ = 0.15406 nm). The diffractogram was scanned in the ranges from 2-10°C at a scan rate of 1°C min⁻¹.

RESULTS AND DISCUSSION

Fourier transform infrared spectroscopy: Fourier Transform Infrared (FTIR) spectroscopy is a useful technique to verify the presence of TOA+, TPA+ and TEA+ in the clay, respectively. Figure 1a-c show, the FTIR spectra of Na-MMT, pure TOA and TOA-MMT, Fig. 2a-c show, the FTIR spectra of Na-MMT pure TPA and TPA-MMT, pure TPA and TPA-MMT and Fig. 3a-c show, the FTIR spectra of Na-MMT, pure TEA and TEA-MMT, respectively. The infrared spectrum of the Na-MMT shows two peaks, which correspond to Si-O stretching at 1040 cm⁻¹ and interlayer water deformation vibrations at 1642 cm⁻¹ (Guo *et al.*, 2006). The band at

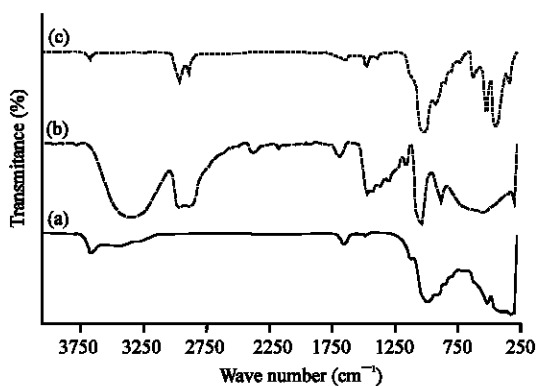


Fig. 1: FTIR Spectra of (a) Na-MMT; (b) TOA and (c) TOA-MMT

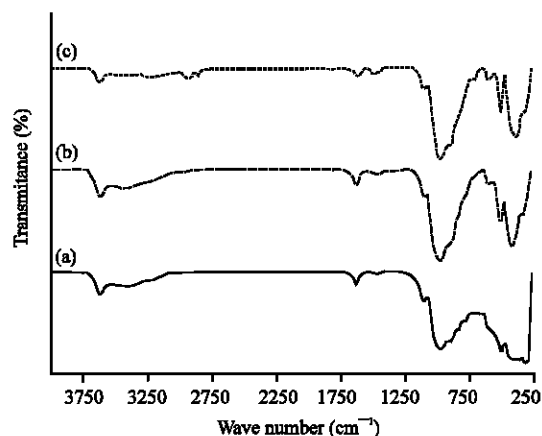


Fig. 3: FTIR spectra of (a) Na-MMT; (b) TEA and (c) TEA-MMT

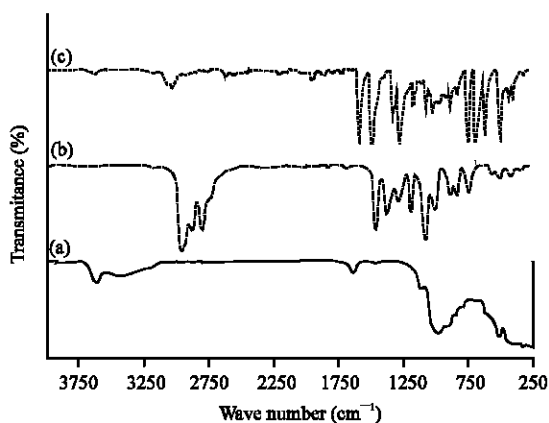


Fig. 2: FTIR spectra of (a) Na-MMT; (b) TPA and (c) TPA-MMT

3630 cm^{-1} results from the O-H stretching vibration. The peaks observed in the TOA-MMT (2926 and 2856 cm^{-1}), TPA-MMT (2923-2851 cm^{-1}) and TEA-MMT (2928 and 2854 cm^{-1}) infrared spectra correspond to the presence of the C-H asymmetric and symmetric stretching vibration, respectively.

In the spectra of TOA-MMT, TPA-MMT and TEA-MMT, The absorption bands at 3628, 3624, 3619 cm^{-1} indicate the presence of the free O-H stretching and at 1077, 1074 and 1071 cm^{-1} corresponded to C-N stretching, respectively (Shalaby *et al.*, 2000; Ramachandran *et al.*, 2007). This suggests that TOA, TPA and TEA are sorbed into the silicate layers of Na-MMT.

X-Ray diffraction analysis: The alkyl ammonium cation exchange enables the conversion of the hydrophilic interior clay surface into the hydrophobic surface and consequently increase the layer distance as well (Liu and Wu, 2001). In this study, Na-MMT was surface treated with TOA, TPA and TEA as intercalation agent

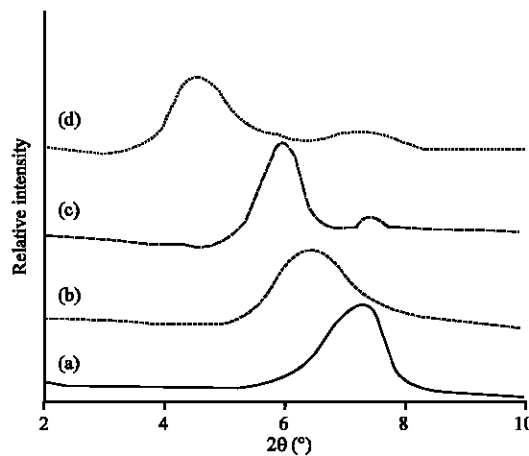


Fig. 4: The XRD patterns of (a) Na-MMT; (b) TEA-MMT, (c) TPA-MMT and (d) TOA-MMT

through cation exchange process. The cationic head groups of the intercalation agent molecule would preferentially reside at the layer surface and the aliphatic tail will radiate a ways from the surface. The presence of these aliphatic chains in the galleries makes the originally hydrophilic silicate to organophilic and thus, increases the layer-to-layer spacing of Na-MMT (Huang *et al.*, 2001). The obtained TOA-MMT, TPA-MMT and TEA-MMT were studied by using X-ray diffraction measurements in the 2θ ranges from 2° - 10° . Na-MMT shows a d_{001} diffraction peak at $2\theta = 7.35^\circ$ which, assigns to the interlayer distance of the natural montmorillonite with a basal spacing of 12.2Å as known in Fig. 4 (Agag and Takeichi, 2001). After the ion exchange reaction, the basal spacing (d_{001} value) increases from 12.2-14.2 Å (Fig. 4a), 15.1 and 19.5Å (Fig. 4b-d) for TEP-MMT, TPA-MMT and TOA-MMT,

Table 2: Diffraction angle and basal spacing of montmorillonite and modified montmorillonite with different organic cations

| Samples | Exchanged cation | 2θ(°) | d(001) spacing (Å) |
|-----------------|--|-------|--------------------|
| Montmorillonite | Na ⁺ | 7.35 | 12.2 |
| TEA modified | (C ₂ H ₅) ₃ NH ⁺ | 6.31 | 14.2 |
| TPA modified | (C ₃ H ₇) ₃ NH ⁺ | 5.93 | 15.1 |
| TOA modified | (C ₈ H ₁₇) ₃ NH ⁺ | 4.59 | 19.5 |

Table 3: C, N and alkylammonium groups contents of the TEA, TPA and TOA modified Montmorillonite

| Alkylammonium/ groups modified/ montmorillonite | Mmol of alkylammonium/ groups/1 g montmorillonite | | Calculation based on C | Calculation based on N |
|---|--|-------|---------------------------|---------------------------|
| | C (%) | N (%) | | |
| TEA | 20.36 | 3.96 | 2.827 | 2.823 |
| TPA | 21.57 | 2.799 | 1.997 | 1.999 |
| TOA | 23.34 | 1.133 | 0.810 | 0.809 |

respectively, suggesting that the TEP⁺, TPA⁺ and TOA⁺ have been intercalated into the Na-MMT galleries. These results were summarized in Table 2. Thus, X-ray diffraction results indicate that TEA, TPA and TOA are successfully intercalated into the silicate layer.

CHNS analysis: Table 3 shows, the results of C and N analysis of the TEA, TPA and TOA modified Montmorillonite. The high contents of C and N in all samples indicate that TEA, TPA and TOA cations were successfully exchanged into the clay. It also shows that 2.827 mol of TEA, 1.997 mol of TPA and 0.810 mol of TOA are sorbed by 1 g of the clay based on C calculations and 2.823, 1.999 and 0.809 mol TEA, TPA and TOA, respectively, based on N calculations. Satisfactory cation exchange of Na⁺ ion in clay with amines was reported by Takeichi *et al.* (2002).

CONCLUSION

Three new organic cations including TEA, TPA and TOA were used to modify Montmorillonite clay in an attempt to create susceptible clay to polymers. The organoclays were characterized using FTIR, XRD and CHNS.

Based on results of this study, the following conclusions can be drawn:

- The three organic cations can be successfully incorporated in the montmorillonite clay
- The basal spacing of the montmorillonite clay increases as a result of incorporating TEA, TPA and TOA
- The incorporation of TEA, TPA and TOA increases the basal spacing by 14.2, 15.1 and 19.5, respectively
- The new organoclay can be susceptible to polymers

ACKNOWLEDGMENTS

The researchers would like to thank Department of Chemistry, Faculty of Science, Putra Malaysia University for the consistent help and support provided during the preparation of this research.

REFERENCES

Agag, T. and T. Takeichi, 2001. Polybenzoxazine-montmorillonite hybrid nanocomposite: Synthesis and characterization. *Polymer*, 41: 7083-7090.

Arroyo, M., M.A. Lopez-Manchado and B. Herreno, 2003. Organo-montmorillonite as substitute of carbon black in natural rubber compounds. *Polymer*, 44: 2447-2453.

Chen, D., J.X. Zhu, P. Yuan, S.J. Yang, T.H. Chen and H.P. He, 2008. Preparation and characterization of anion-cation surfactants modified montmorillonite. *J. Therm. Anal. Calorim.*, 94: 841-848.

Guo, L., S. Wu, F. Zeng and J. Zhao, 2006. Synthesis and fluorescence property of terbium complex with novel Schiff-base macromolecular ligand. *Eur. Polym. J.*, 42: 1670-1675.

He, H.P., D. Yang, P. Yuan, W. Shen and R.L. Frost, 2007a. TEM, XRD and thermal stability of adsorbed paranitrophenol on DDOAB organoclay. *J. Colloid Interface Sci.*, 311 (1): 24-37.

He, H.P., J.G. Guo, X.D. Xie and J.L. Peng, 2007b. *Environ. Int.* Grafting of montmorillonite with different functional silanes via two different reaction systems. *J. Colloid Interface Sci.*, 313 (1): 268-273.

Huang, J., Z. Zhu, J. Yin, X. Qian and Y. Sun, 2001. Poly(etherimide)/montmorillonite nanocomposites prepared by melt intercalation: morphology, solvent resistance properties and thermal properties. *Polymer*, 42: 873-877.

Jaynes, W.F. and S.A. Boyd, 1991. Clay mineral type and organic compound sorption by hexadecyltrimethyl ammonium exchanged clays. *Soil Sci. Soc. Am. J.*, 55: 43-48.

Kim, J.H., W.S. Shin, Y.H. Kim, S.J. Choi, Y.W. Jeon and D.I. Song, 2003. Structure of organoclays an X-ray diffraction and thermogravimetric analysis study. *J. Colloid Interface Sci.*, 47: 59-64.

Kojima, Y., A. Usuki, M. Kawasumi, A. Okada, Y. Fukushima, T. Karauchi and O. Kamigaito, 1993. Mechanical properties of nylon-6/clay hybrid. *J. Mater. Res.*, 6: 1185-1189.

Lagaly, G., 1986. Interaction of alkylamines with different types of layered compounds. *Solid State Ionics*, 22: 43-51.

Liu, X. and Q. Wu, 2001. PP/clay nanocomposites prepared by grafting melt intercalation. *Polymer*, 42: 10013-10019.

- Maiti, M. and A.K. Bhowmick, 2005. Structure and properties of some novel fluoroelastomer/clay nanocomposites with special reference to their interaction. *J. Applied Polym. Sci.*, 44: 162-176.
- Magaraphan, R., W. Lilayuthalert and A. Sirivat, 2001. Preparation, structure, properties and thermal behaviour of rigid-rod polyimide/montmorillonite nanocomposites. *Composites Sci. Technol.*, 61: 1253-1264.
- Rajkiran, R.T. and C.K. Kartic, 2008. Upendra Natarajan. Synthesis and characterization of novel organo-montmorillonites. *Applied Clay Sci.*, 38: 203-208.
- Ramachandran, E., K. Baskaran and S. Natarajan, 2007. XRD, thermal, FTIR and SEM studies on gel growing glycine crystals. *Cryst. Res. Technol.*, 42 (1): 73-77.
- Shalaby, A.M., O.A. Fathalla, E.M.M. Kassem and M.E. A. Zaki, 2000. Synthesis of new 5-N-pyrazolyl amino acids, pyrazolopyrimidines and pyrazolopyrimidines derivatives. *Acta Chim. Slov.*, 47: 187-203.
- Stretz, H.A., D.R. Paul, R. Lib, H. Keskkula and P.E. Cassidy, 2005. Intercalation and exfoliation relationships in melt-processed poly (styrene-co-acrylonitrile)/montmorillonite nanocomposites. *Polymer*, 46: 2621-2637.
- Takeichi, T., R. Zeidam and T. Agag, 2002. polybenzoxazine/clay hybrid nanocomposites: Influence of preparation method on the curing behaviour and properties of polybenzoxazines. *Polymer*, 43: 45-53.
- Xie, W., Z. Gao, K. Liu, W. Pan, R. Vaia, D. Hunter and A. Singh, 2001. Thermal characteristic of organomodified montmorillonite. *Thermochimica Acta*, 367: 339-350.
- Zhang, J. and C.A. Wilkie, 2003. Preparation and flammability properties of polyethylene-clay nanocomposites. *Polym. Degrad. Stability*, 80: 163-169.